

<https://doi.org/10.15407/ujpe63.3.245>

M.I. GOROBETS, S.A. KIRILLOV

Joint Department of Electrochemical Energy Systems, Nat. Acad. of Sci. of Ukraine  
(38A, Vernadsky Ave., Kyiv 03142, Ukraine; e-mail: kir@i.kiev.ua)

## PICOSECOND DYNAMICS OF MOLECULAR ENTITIES IN LITHIUM SALT SOLUTIONS IN DIMETHYL SULFOXIDE, PROPYLENE CARBONATE, AND DIMETHYL CARBONATE

*An analysis of the Raman spectra of solutions of lithium salts in dimethyl sulfoxide, propylene carbonate, and dimethyl carbonate in a concentration range from diluted solutions to the mixtures of molten solvates with salts has been performed in terms of the dynamics, specifically, dephasing ( $\tau_V$ ) and modulation ( $\tau_\omega$ ) times of all molecular entities present in solutions are determined and analyzed. It has been found that, in the picosecond time domain, dephasing and modulation in solvent molecules hydrogen-bonded with an anion and/or solvating a cation are slower than in free solvent molecules. In solvent separated ion pairs, both  $\tau_V$  and  $\tau_\omega$  are much longer than in solvated anions, thus indicating strong interactions between anions and their surrounding. In contact ion pairs,  $\tau_V$  are great, whereas  $\tau_\omega$  appear close to those for free anions. This reflects that the structure of the liquid tends to the structure of molten salts.*

*Keywords:* Raman spectra, solvation, ion pairs, dephasing, modulation.

### 1. Introduction

Vibrational spectroscopy is widely used for recognizing solvation and formation of solvent-separated (SSIP) and contact (CIP) ion pairs in ionic solutions [1]. In spite of the fact that vibrational spectroscopy approaches are considered a powerful tool for studying interparticle interactions and dynamics in ionic systems [2–4], not so much work has been done in the past so as to uncover the nature of solvates and ion pairs. The first studies of the dynamics of solvent molecules surrounding cations in lithium salt solutions in pyridine and acetone performed by means of line profile analysis have shown a decrease in characteristic times of vibrational dephasing upon the solvation [5, 6]. A similar observation follows for lithium salt solutions in dimethylsulfone [7]. The ion pair formation has been treated in terms of dynamics in nitrate and perchlorate solutions in water and non-aqueous solvents [8–11]. It has been found that, for the anions in SSIPs and CIPs, the dephasing process is more rapid as compared to the solvated anions. In studies of specific solvation of molecular anions via hydrogen bonding carried out in pump-probe experiments [12], the rapid vibrational energy relax-

ation has appeared characteristic of strong coupling between the anions and the solvents, while longer vibrational energy relaxation reveals weaker solvent interactions.

Nowadays, the interest in the study of dynamics of lithium salts in various solvents is renewed, especially due to a particular attention paid by electrochemists to concentrated solutions of lithium salts [13]. In recent years, dynamics in lithium salt solutions has been studied by various methods, including coherent two-dimensional infrared spectroscopy and pump-probe experiments [14–17]. In Ref. [14], investigations of dynamics of  $\text{LiPF}_6$  solutions in butylene carbonate and dimethyl carbonate have been conducted, by using steady-state and two-dimensional infrared spectroscopies. It has been found that the addition of a salt induces a slowdown of the motions of solvent molecules, because the presence of ions imposes a strong ordering through ion dipole interactions (solvation shell) and Coulombic interactions between the charged species. Time resolved experiments reveal that the solvation shell formed by cyclic carbonates is more rigid than that formed by linear carbonates. The study of the ultrafast carbonate solvent exchange dynamics around lithium ions in carbonate solutions with coherent two-dimensional infrared spec-

troscopy [15] demonstrates that the time constants of the formation and dissociation of the lithium-ion – carbonate complex in solvation sheaths are on a picosecond time scale, and the vibrational lifetime of the Li diethyl carbonate complex is found to be much shorter than that of a free solvent. Molecular rotation measurements of lithium salts in solvents containing a C–N group [16, 17] show that the anisotropy decay of the solvent bound to  $\text{Li}^+$  is much slower than that of a free solvent molecule, and the lifetime of the cation solvate was determined.

In spite of some progress in this field, the problem of dynamic criteria of the cation solvation and the ion pairing is far from being settled. Unlike the situation with a specific solvation via the hydrogen bonding, where clear dynamic signatures are established, the data on the dynamics in ionic solutions need to be specified and systematized. In order to make a step in this direction, this paper deals with the Raman data on the solvation and ion pairing in solutions of various lithium salts in dimethyl sulfoxide (DMSO), propylene carbonate (PC) and dimethyl carbonate (DMC) in a concentration range from 0.05 to 0.25 mole fractions of a salt, from diluted solutions to the mixtures of molten  $\text{LiX} \times 4\text{S}$  solvates with  $\text{LiX}$ , where X is the anion [18, 19], and treats this data from the point of view of dynamics.

One of the simplest and well-established methods of studying the dynamics in condensed media is the analysis of line profiles in terms of vibrational relaxation phenomena of probe molecules. The time correlation function (TCF)  $G_V(t)$  is determined by the Fourier transformation of the isotropic  $I_{\text{iso}}(\nu)$  Raman spectrum [20–22],

$$G_V(t) = \int_{-\infty}^{+\infty} I_{\text{iso}}(\nu) \exp(2\pi i c \nu t) d\nu, \quad (1)$$

where  $c$  is the speed of light, and  $\nu$  is the frequency measured in wavenumbers. Among various mechanisms of vibrational relaxation, the main cause for the broadening of isotropic lines in Raman spectra is the vibrational dephasing [20–22] with a characteristic time  $\tau_V = \int G_V(t) dt$ . It arises due to the adiabatic perturbations of the probe molecule by its surrounding. These perturbations modulate the molecular vibrations and lead to phase shifts. The TCF of the vibrational dephasing is described by the Kubo equa-

tion [23],

$$G_V(t) = M_2 \tau_\omega^2 e^{-\exp(-t/\tau_\omega) - 1 + t/\tau_\omega}, \quad (2)$$


where  $\tau_\omega$  is the modulation (perturbation) time and  $M_2 = \int \nu^2 I_{\text{iso}}(\nu) d\nu / \int I_{\text{iso}}(\nu) d\nu$  is the vibrational second moment. If  $\tau_\omega \rightarrow 0$  (perturbations are weak and fast, interactions are nonspecific, the surrounding of a probe molecule is flexible), the TCFs are exponential, and the spectra have a Lorentzian shape. In this case, the modulation phenomenon is described in terms of collision concepts and is considered to be collision-driven, and  $\tau_\omega$  may be equated to the time between collisions  $\tau_{BC}$  of the probe particle with neighboring particles. If  $\tau_\omega \rightarrow \infty$  (perturbations are strong and slow, the interactions are specific and directed, the particle and its surrounding form a rigid quasilattice), the shape of the TCFs and the spectra become Gaussian. Just these principles are used in what follows.

## 2. Experimental

$\text{LiBF}_4$  (Novosibirsk, Russia, 99.98%),  $\text{LiClO}_4$  (Novosibirsk, Russia, 99.98%),  $\text{LiCF}_3\text{SO}_3$  (Fluka, 62621, 99.5%),  $\text{LiN}(\text{CF}_3\text{SO}_2)_2$  (Fluka, 15224, 99.95%), and  $\text{LiB}(\text{C}_2\text{O}_4)_2$  (Novolite, 99.9%) were dried in vacuum at 150 °C for 24 hours. DMSO (Aldrich, 276855,  $\geq 99.9\%$ , melting point 18.5 °C), PC (Aldrich, 310328, melting point –48.8 °C), and DMC (Aldrich, 517127, melting point 4.6 °C) were used without further treatment. Solutions containing 0.05, 0.1, 0.15, 0.2, and 0.25 mole fraction of the salt were prepared by mixing the proper amounts of salt and solvent in a dry glovebox. Remaining humidity in the glovebox was monitored with a digital hygrometer. All preparation procedures were described in more detail in Ref. [24]. For the investigation of Raman spectra, solutions were flame-sealed in Pyrex tubes with an inner diameter of 5 mm.

A method to obtain Raman spectra is described in Refs. [18, 25] in detail. Since all the lines studied are sharply polarized, only isotropic spectra are presented in what follows. The decomposition of overlap lines and calculations of TCFs have been performed in terms of an analytical method suggested in Ref. [26] and reviewed in Refs. [3, 4].

The Raman spectra of  $\text{LiBF}_4$ ,  $\text{LiCF}_3\text{SO}_3$ ,  $\text{LiN}(\text{CF}_3\text{SO}_2)_2$ , and  $\text{LiB}(\text{C}_2\text{O}_4)_2$  in DMSO were recorded at 50 °C, and the  $\text{LiClO}_4$ -DMSO system

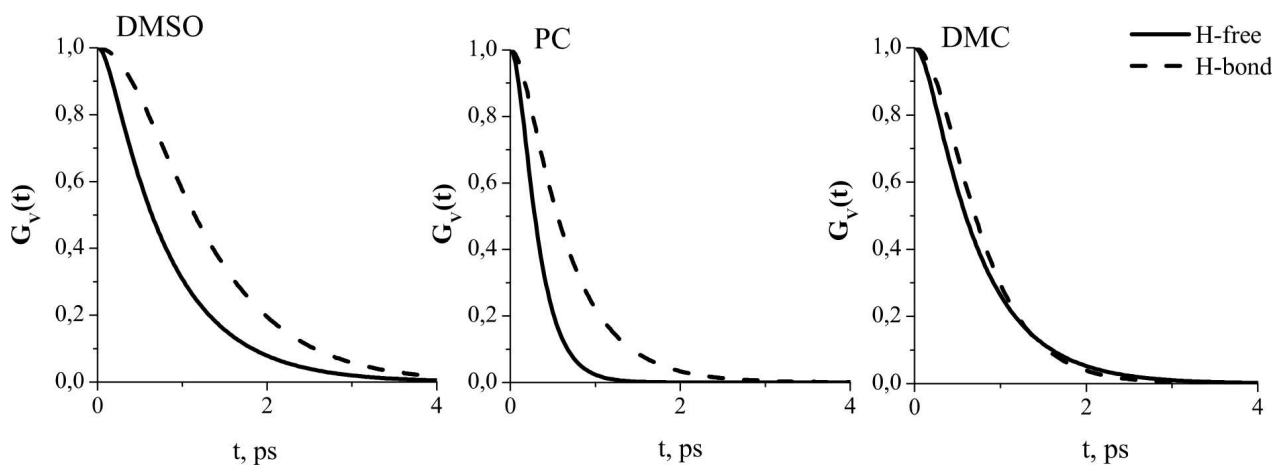

**Fig. 1.** TCFs of dephasing of hydrogen-bond-free solvent molecules and solvent molecules hydrogen-bonded with anion in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

at 90 °C, since these are the minimal possible temperatures for studying the whole concentration range of these systems in the liquid state. The  $\text{LiClO}_4$  spectra in PC and DMC were registered at ambient temperature. For more detail regarding the assignment of vibrational lines and their choice for the solvation and ion pairing studies, the concentration dependences of solvation numbers of cations and anions and the content of solvated ions, SSIPs and CIPs in solutions, see Refs. [18, 19].

### 3. Results and Discussion

Aiming at understanding the dynamical signatures of solvation and ion pairing, it would be quite natural to begin with solvation of molecular anions via the hydrogen bonding and to compare the results obtained with conclusions drawn in pump-probe experiments [12]. In order to do so, vibrations involving the hydrogen atoms of  $\text{CH}_3$ -groups have been analyzed. In the  $\text{CH}_3$ -groups, the positive charge is localized on the hydrogen atoms. Hence, O or F atoms of an anion interact with the hydrogen of a methyl group of the solvent molecule, forming the so-called “blue-shifting” hydrogen bond [27–29].


As follows from our work [30], in the neat DMSO, the line at  $\sim 2913 \text{ cm}^{-1}$  corresponding to the  $\text{CH}_3$  symmetric stretch  $\nu_3 (A')$  is single, has a symmetric profile, and demonstrates no evidences of hydrogen bonding between DMSO molecules. From the point of view of dimerization processes, the absence of its splitting means that the perturbations of  $\text{CH}_3$ -

groups in the monomers and dimers are of the same value, and, in this spectral region, the monomers and dimers are indistinguishable in Raman spectra. The analysis of the spectra of lithium salt solutions in DMSO in the region shows the presence of the non-bonded DMSO molecules ( $\sim 2919 \text{ cm}^{-1}$ ) and the solvent molecules entering the solvation sphere of an anion and hydrogen-bonded to it ( $\sim 2913 \text{ cm}^{-1}$ ) [25].

The line at  $\sim 2930 \text{ cm}^{-1}$  corresponding to the symmetric  $\text{CH}_3$  stretch  $\nu_{14} (A_1)$  in the neat PC is split into two components at 2930 and  $2941 \text{ cm}^{-1}$  corresponding to hydrogen-bond-free molecules and to molecules hydrogen-bonded to anions [31]. Upon adding the salt, the intensity of the component at  $\sim 2941 \text{ cm}^{-1}$  increases, and the intensity of the component at  $\sim 2930 \text{ cm}^{-1}$  decreases [25, 32].

Like in DMSO, the line at  $\sim 2960 \text{ cm}^{-1}$  corresponding to the symmetric  $\text{CH}_3$  stretch  $\nu_2 (A_1)$  of the cis conformer of the neat DMC [29] shows no evidence of the hydrogen bonding. The behavior of the  $\nu_2 (A_1)$  vibration in the salt solutions in DMC is similar to that of  $\text{CH}$ -vibrations in DMSO solutions [25]. The split lines can be assigned to the non-bonded DMC molecules ( $\sim 2919 \text{ cm}^{-1}$ ) and the solvent molecules entering the solvation sphere of the anion and hydrogen-bonded to it ( $\sim 2913 \text{ cm}^{-1}$ ) [25, 34, 35].

Respective TCFs are shown in Fig. 1. Calculations reveal that, as expected, in hydrogen-bond-free solvent molecules, dephasing and modulation are faster than in solvent molecules hydrogen-bonded with

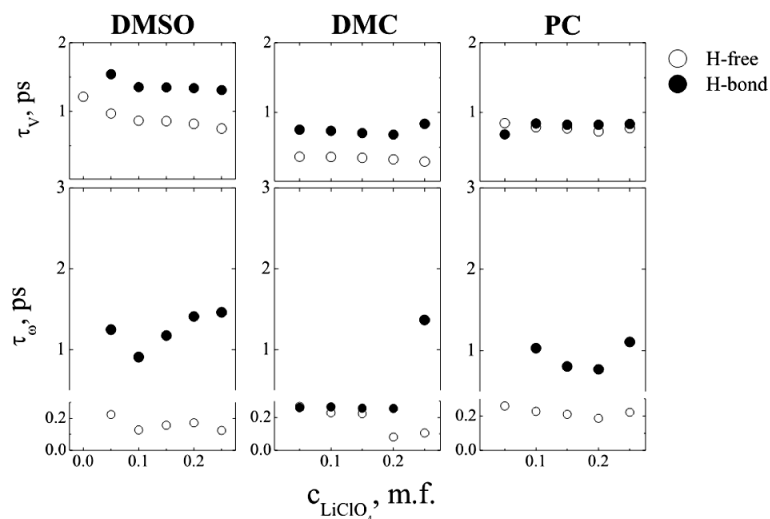

**Fig. 2.** Dephasing and modulation times for free solvent molecules and solvent molecules hydrogen-bonded with anions in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

anions (Fig. 2). It can also be noted that, for the hydrogen-bond-free solvent molecules, the TCFs are close to exponential, and the spectra have a more Lorentzian shape, as opposed to the solvent molecules hydrogen-bonded with anions, for which the shape of the TCFs and the spectra become more Gaussian.

Now, let us turn to cation solvation effects. In DMSO, these have been studied by the analysis of the isotropic line corresponding to the symmetric CS stretching  $\nu_{10}$  ( $A'$ ) vibration. In the Raman spectra of pure liquid DMSO, this line is split into two components at  $\sim 665$  and  $\sim 669$   $\text{cm}^{-1}$ , which reflects the presence of monomeric molecules and cyclic dimers [30]. When lithium salts are added, the Raman spectra of DMSO undergo changes. From our recent studies [25], a composite line in the region of the  $\nu_{10}$  ( $A'$ ) vibration can be decomposed into three components, the first two corresponding to the vibrations of monomeric ( $\nu = 663$ – $670$   $\text{cm}^{-1}$ ) DMSO molecules and DMSO dimers ( $\nu = 667$ – $669$   $\text{cm}^{-1}$ ), and the new component at higher wavenumbers ( $\nu = 674$ – $676$   $\text{cm}^{-1}$ ) corresponding to particles entering the solvation shell of cations [36–39].


The ordering in PC is also seen in the Raman spectra as splitting of the line corresponding to the  $\nu_{10}$  ( $A_1$ ) symmetric vibrations of a PC ring,  $\nu \sim 706$   $\text{cm}^{-1}$  for monomers, and  $\nu \sim 710$   $\text{cm}^{-1}$  for dimers [40, 41]. In the presence of lithium salts, the line of  $\nu_{10}$

( $A_1$ ) vibrations can be decomposed into three components reflecting the presence of monomeric ( $\nu = 706$ – $707$   $\text{cm}^{-1}$ ), dimeric ( $\nu = 711$ – $712$   $\text{cm}^{-1}$ ), and solvating ( $\nu = 716$ – $717$   $\text{cm}^{-1}$ ) PC molecules [25].


As to DMC, the presence of monomers ( $\nu \sim 513$   $\text{cm}^{-1}$ ) and cis-cis dimers ( $\nu \sim 516$   $\text{cm}^{-1}$ ) is noticeable in the Raman spectrum in the region of  $\nu_9$  ( $A_1$ ) O–C–O bond vibrations [33]. When lithium salts are added, the  $\nu_9$  ( $A_1$ ) line can be decomposed into three components corresponding to monomeric ( $\nu = 513$ – $515$   $\text{cm}^{-1}$ ), dimeric ( $\nu = 516$ – $517$   $\text{cm}^{-1}$ ), and solvating ( $\nu = 523$   $\text{cm}^{-1}$ ) DMC molecules [25].

The time correlation functions of the vibrational dephasing of the monomeric, dimeric, and solvating molecules in DMSO, PC, and DMC are shown in Fig. 3. The analysis of characteristic times (Fig. 4) reveals that, for both associated (dimeric) and solvating molecules of the solvent in the systems studied, the vibrational dephasing is slow, and its speed is approximately equal to the modulation speed. This contrasts with the rapid modulation process for monomeric solvent molecules, which should be considered collision-driven. Such situation closely resembles relations between characteristic times in the case of anion solvation described above.

The “bonded” solvent molecules are located near their neighbors. When the bonds between them are disrupted (characteristic time  $\tau_\omega$ ), phase shifts (characteristic time  $\tau_V$ ) take place. The relation  $\tau_V \approx \tau_\omega$

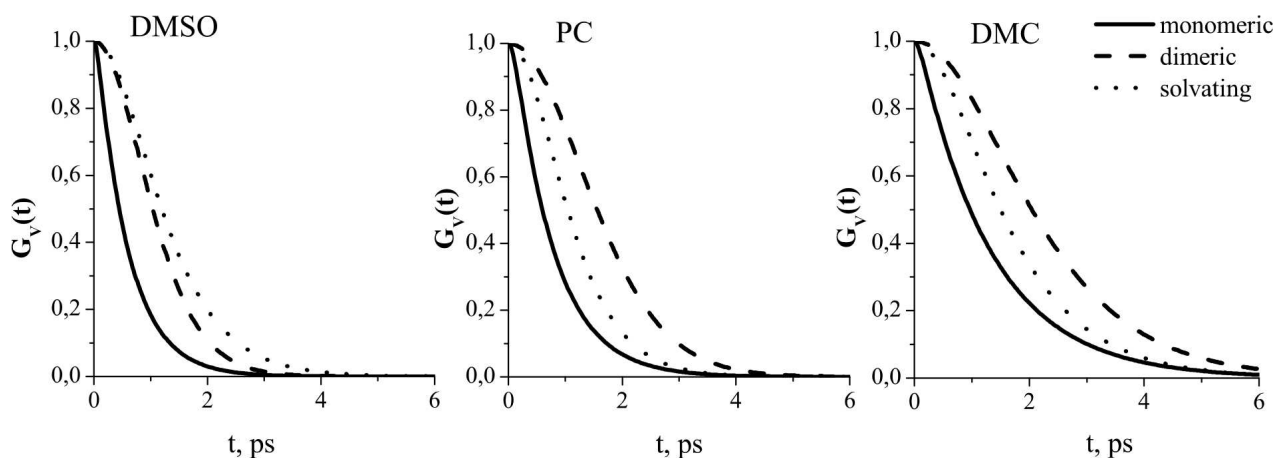

**Fig. 3.** TCFs of the dephasing of monomeric, dimeric, and solvating solvent molecules in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

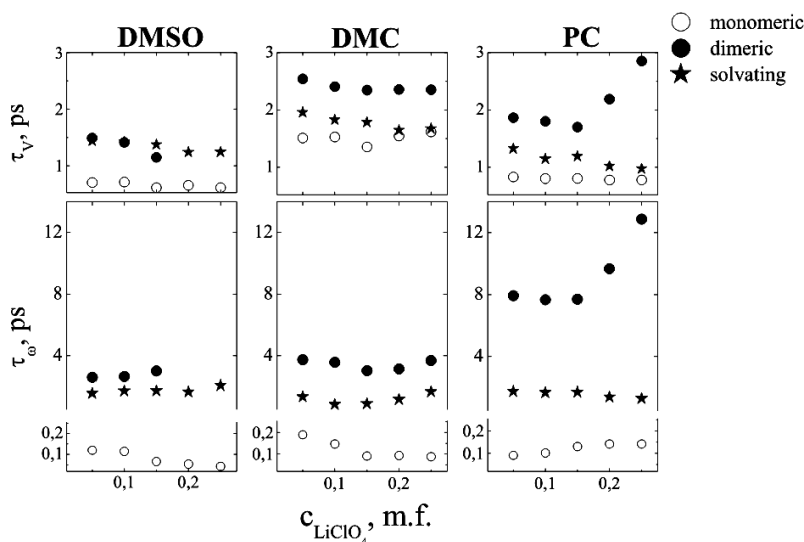

**Fig. 4.** Dephasing and modulation times for monomeric, dimeric, and solvating solvent molecules in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

may be considered as an evidence of the close stability of both associates and solvation complexes in the solutions studied. From the point of view of the dynamic criteria of complex formation [44, 45], the lower limit of the lifetime of solvation spheres surrounding  $\text{Li}^+$  ions is equal to  $\tau_\omega \approx \tau_V \sim 1.5$  ps, and the solvated complexes should be considered long-lived, at least, in the picosecond time domain. The TCFs for the “bonded” solvent molecules become more Gaussian, while the TCFs for monomeric solvent molecules are close to exponential, and the respective components have more Lorentzian shape.

Signatures of ion pairing in solutions are seen, first of all, as extra lines appearing in the vicinity of intense lines corresponding to non-degenerated vibrations of anions. Upon adding  $\text{LiBF}_4$  to DMSO, the  $\nu_1$  line of  $\text{BF}_4^-$  splits into three components at 760, 763, and 768  $\text{cm}^{-1}$ , which can be assigned to anions in the free state, in SSIPs, and in CIPs, respectively [25, 46, 47]. The integrated intensities of the component lines vary with the salt concentration. If the salt content is growing, the intensity of the component corresponding to free ions passes a maximum, and, at 0.25 mole fraction of the salt, becomes negligible. SSIPs

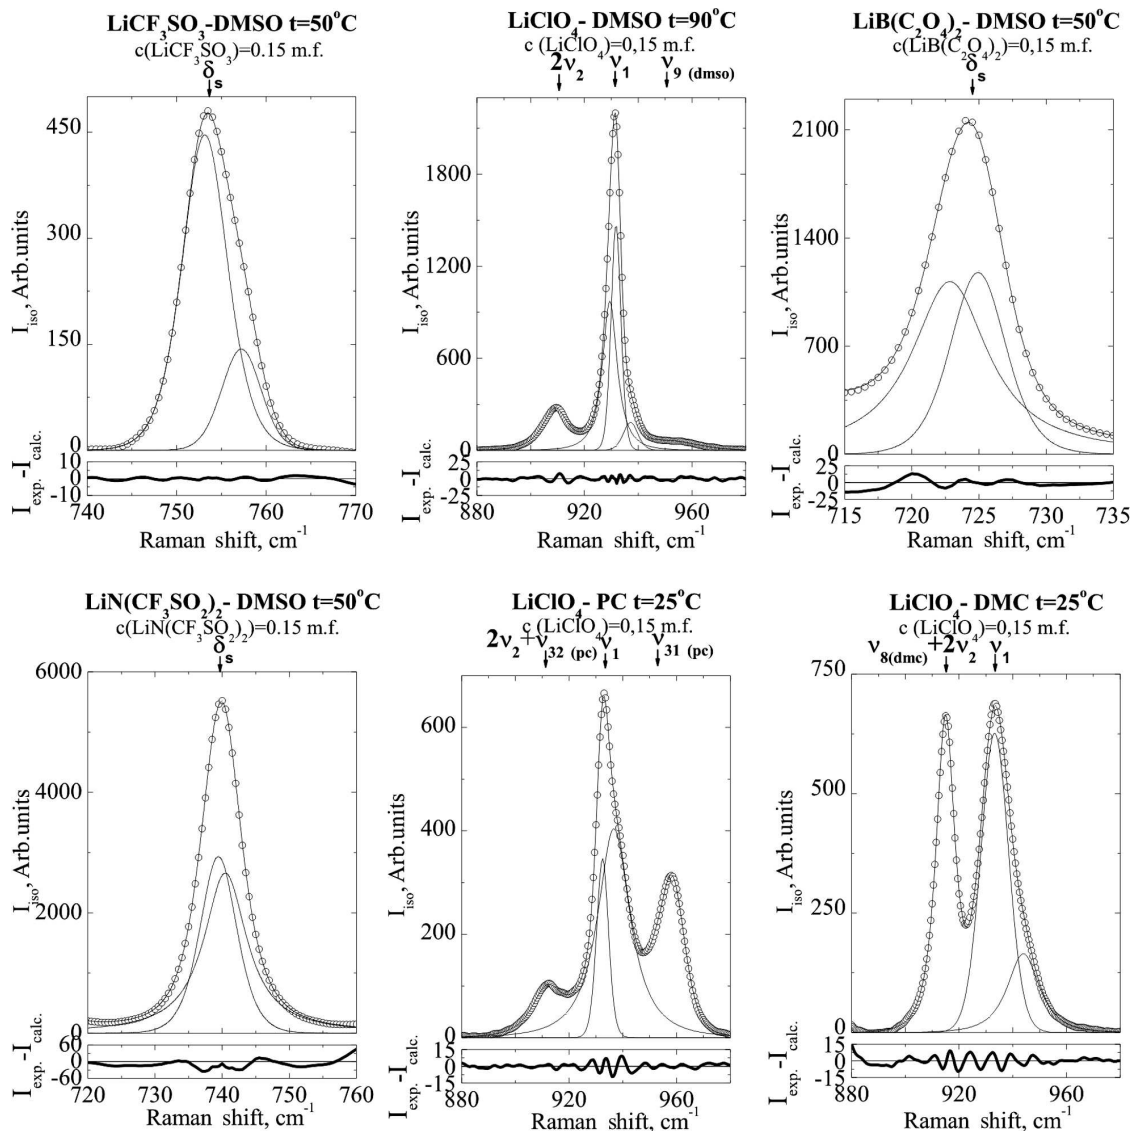



Fig. 5. Raman spectra of lithium salt solutions in DMSO, PC, and DMC in regions sensitive to the ion pairing

are present in solutions at all concentrations studied. CIPs become visible at 0.15 mole fraction of the salt [19].


In solutions of  $\text{LiCF}_3\text{SO}_3$  in DMSO, the line corresponding to the  $\delta_s$  ( $A_1$ )  $\text{CF}_3$  vibrations of the anion is split into three components at 753, 758, and  $762\text{ cm}^{-1}$  attributed to free anions, SSIPs, and CIPs, respectively (Fig. 5) [48, 49]. The intensity of the components attributed to free anions increases with the salt concentration, SSIPs become visible at 0.1 mole fraction of the salt, and CIPs appear in

more concentrated solutions containing 0.2 mole fraction of  $\text{LiCF}_3\text{SO}_3$ . A similar behavior is characteristic of  $\text{LiClO}_4$ -DMSO solutions (Fig. 5). The  $\nu_1$  line of  $\text{ClO}_4^-$  splits into three components at 929, 932, and  $937\text{ cm}^{-1}$  corresponding to anions in the free state, in SSIPs, and in CIPs, respectively [50–52]. In this system, free ions and SSIPs are present in all solutions, and CIPs exist in solutions containing more than 0.1 mole fraction of  $\text{LiClO}_4$ .

Unlike three previous systems, Raman spectra in the ion-pairing sensitive region of solutions of

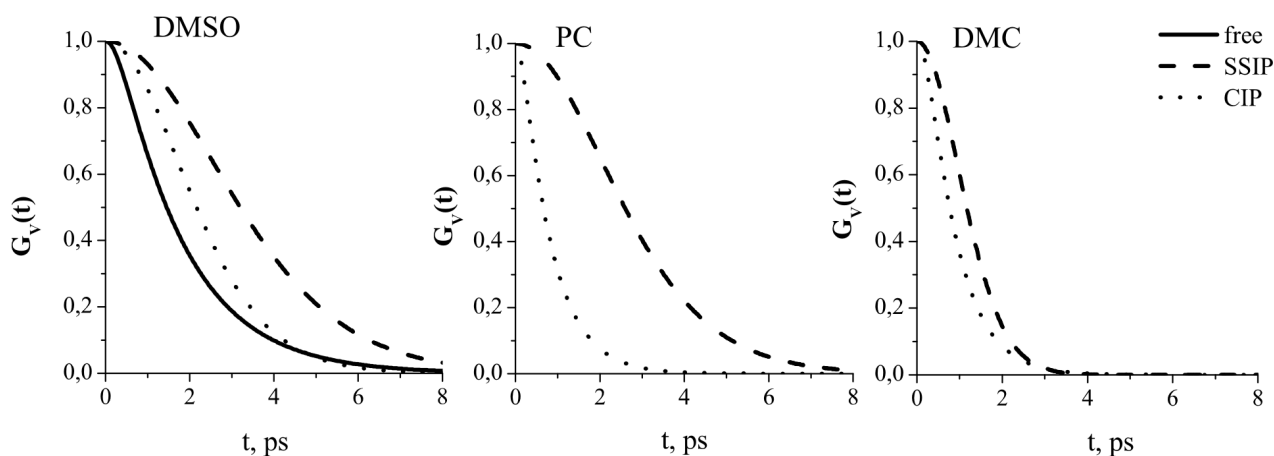

**Fig. 6.** TCFs of the dephasing of  $\text{ClO}_4^-$  anion in the free state, SSIPs, and CIPs in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

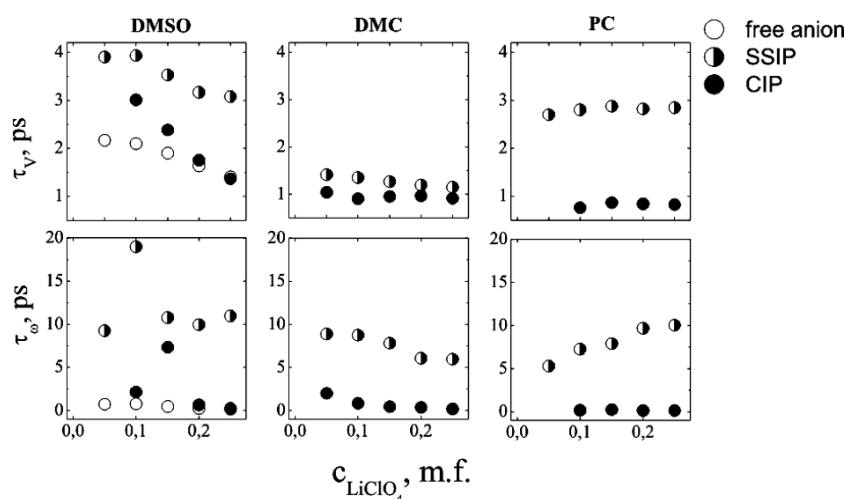

**Fig. 7.** Dephasing and modulation times for a  $\text{ClO}_4^-$  anion in the free state, SSIPs, and CIPs in  $\text{LiClO}_4$  solutions in DMSO, PC, and DMC

$\text{LiB}(\text{C}_2\text{O}_4)_2$  and  $\text{LiN}(\text{SO}_2\text{CF}_3)_2$  in DMSO are split into two components (Fig. 5) and do not demonstrate the presence of CIPs. The line corresponding to the  $\delta_s$  ( $A_1$ ) O–B–O vibrations of  $\text{B}(\text{C}_2\text{O}_4)_2^-$  can be decomposed into components at 723 (free anions) and 725  $\text{cm}^{-1}$  (SSIPs). The components of the line corresponding to  $\delta_s$  ( $A_1$ )  $\text{CF}_3$  vibrations of  $\text{N}(\text{SO}_3\text{CF}_3)_2^-$  can be assigned to free anions (741  $\text{cm}^{-1}$ ) and SSIPs (739  $\text{cm}^{-1}$ ). In both systems, free ions are present in all solutions, and SSIPs are visible at the highest dilutions studied (Fig. 5).

The Raman spectra of solutions of  $\text{LiClO}_4$  in PC and DMC and their fits clearly reveal the presence of two types of particles having the lines at

$\nu = 932.5$  and  $937 \text{ cm}^{-1}$  in PC and at  $\nu = 933$  and  $942 \text{ cm}^{-1}$  in DMC (Fig. 5). In PC, the intensity of the low-frequency component increases with the salt concentration, and the high-frequency component is absent in the most diluted solutions. In DMC, the intensity of both components grows upon adding the salt. The low-frequency components can be assigned to anions forming SSIPs and the high-frequency components – to anions in CIPs, respectively [32, 53].

The analysis of TCFs (Fig. 6) and characteristic times (Fig. 7) shows that, in free anions,  $\tau_\omega$  are short and evidence the weak interactions between anions and their environment. In SSIPs,  $\tau_\omega$  are an order of

magnitude longer, by signifying strong interactions between anions and cations. In CIPs showing up in more concentrated solutions,  $\tau_\omega$  becomes shorter than in SSIPs, probably by demonstrating that the structure of concentrated solutions acquires the features of molten salts, for which short  $\tau_\omega$  are quite obvious [2]. Moreover, when passing from the solvated anion to the SSIP, the Raman profiles of anion lines are transformed from Lorentzian to Gaussian form, and passing from SSIP to the CIP – from Gaussian to Lorentzian form.

#### 4. Conclusion

In this paper, the analysis of the Raman spectra of various lithium salt solutions in DMSO, PC, and DMC in a concentration range from diluted solutions to the mixtures of molten solvates with salts has been performed in terms of the dynamics. The TCFs of vibrational dephasing and respective dephasing and modulation times of all molecular entities present in solutions have been determined. It has been found that, in the picosecond time domain, dephasing and modulation in solvent molecules hydrogen-bonded with anions and/or solvating cations are slower than in free solvent molecules. In SSIPs, both dephasing and modulation times are much longer than in solvated anions. The slowing-down of dephasing and collisions indicates strong interactions between anions and their surrounding. At low concentrations of CIPs, the dephasing times are great, at high concentrations these get shorter, whereas modulation times become close to those for free anions. This reflects that the structure of the liquid tends to the structure of molten salts.

1. J.M. Alía. Raman spectroscopic studies of ion-ion interactions in aqueous and nonaqueous electrolyte solutions. In *Handbook of Raman Spectroscopy, from the Research Laboratory to the Process Line*, edited by I.R. Lewis, H.G.M. Edwards (Marcel Dekker, 2001) [ISBN: 0-8247-0557-2].
2. S.A. Kirillov. Interactions and picosecond dynamics in molten salts: a review with comparison to molecular liquids. *J. Mol. Liquids* **76**, 35 (1998).
3. S.A. Kirillov. Novel approaches in spectroscopy of interparticle interactions. Vibrational line profiles and anomalous non-coincidence effects. In *Novel Approaches to the Structure and Dynamics of Liquids: Experiments, Theories and Simulations*, edited by J. Samios, V. Durov, NATO ASI Series (Dordrecht, 2004), p. 193–227 [ISBN: 978-1-4020-1847-3].
4. S.A. Kirillov. Spectroscopy of interparticle interactions in ionic and molecular liquids: novel approaches. *Pure Appl. Chem.* **76**, 171(2004).
5. I.S. Perelygin, A.S. Krauze. Raman spectra and dynamics of pyridine molecules in ionic solutions. *Khim. Fiz.* **7**, 1231 (1988) (in Russian).
6. I.S. Perelygin, A.S. Krauze. Vibrational and orientational relaxation of acetone molecules in ionic solutions. *Khim. Fiz.* **8**, 1043 (1989) (in Russian).
7. D.O. Tretyakov, V.D. Prisiazhnyi, M.M. Gafurov, K.Sh. Rabadanov, S.A. Kirillov. Formation of contact ion pairs and solvation of  $\text{Li}^+$  ion in sulfones: Phase diagrams, conductivity, Raman spectra, and dynamics. *J. Chem. Eng. Data* **55**, 1958 (2010).
8. R.L. Frost, D.W. James, R. Appleby, R.E. Mayes. Ion-pair formation and anion relaxation in aqueous solutions of Group 1 perchlorates. A Raman spectral study. *J. Phys. Chem.* **86**, 3840 (1982).
9. D.W. James, R.E. Mayes. Ion-ion-solvent interactions in solution. I. Solutions of  $\text{LiClO}_4$  in acetone. *Aust. J. Chem.* **35**, 1775 (1982).
10. D.W. James, R.E. Mayes. Ion-ion-solvent interactions in solution. II. Solutions of  $\text{LiClO}_4$  in diethyl ether. *Aust. J. Chem.* **35**, 1785 (1982).
11. D.W. James, R.E. Mayes. Ion-ion-solvent interactions in solution. 8. Spectroscopic studies of the lithium perchlorate/N,N-dimethylformamide system. *J. Phys. Chem.* **88**, 637 (1984).
12. M. Li, J. Owrutsky, M. Sarisky, J.P. Culver, A. Yodh, R.M. Hochstrasser. Vibrational and rotational relaxation times of solvated molecular ions. *J. Chem. Phys.* **98**, 5499 (1993).
13. Y. Yamada, A. Yamada. Review Superconcentrated electrolytes for lithium batteries. *J. Electrochem. Soc.* **162** A2406 (2015).
14. K.D. Fulfer, D.G. Kuroda. Solvation structure and dynamics of the lithium ion in organic carbonate-based electrolytes: A time-dependent infrared spectroscopy study. *J. Phys. Chem. C* **120**, 24011 (2016).
15. K.K. Lee, K. Park, H. Lee, Y. Noh, D. Kossowska, K. Kwak, M. Cho. Ultrafast fluxional exchange dynamics in electrolyte solvation sheath of lithium ion battery. *Nat. Commun.* **8**, 14658 (2017).
16. Y. Shen, G. Deng, C. Ge, Y. Tian, G. Wu, X. Yang, J. Zheng, K. Yuan. Solvation structure around the  $\text{Li}^+$  ion in succinonitrile-lithium salt plastic crystalline electrolytes. *Phys. Chem. Chem. Phys.* **18**, 14867 (2016).
17. K. Yuan, H. Bian, Y. Shen, B. Jiang, J. Li, Y. Zhang, H. Chen, J. Zheng. Coordination number of  $\text{Li}^+$  in non-aqueous electrolyte solutions determined by molecular rotational measurements. *J. Phys. Chem. B* **118**, 3689 (2014).



18. M.I. Gorobets, M.B. Ataev, M.M. Gafurov, S.A. Kirillov. Raman study of solvation in solutions of lithium salts in dimethyl sulfoxide, propylene carbonate and dimethyl carbonate. *J. Mol. Liq.* **205**, 98 (2015).
19. S.A. Kirillov, M.M. Gafurov, M.I. Gorobets, M.B. Ataev. Raman study of ion pairing in solutions of lithium salts in dimethyl sulfoxide, propylene carbonate and dimethyl carbonate. *J. Mol. Liq.* **199**, 167 (2014).
20. D.W. Oxtoby. Dephasing of molecular vibrations in liquids. *Adv. Chem. Phys.* **40**, 1 (1979).
21. W.G. Rothschild. *Dynamics of Molecular Liquids* (Wiley, 1984) [ISBN: 978-0-4717-3971-5].
22. C.H. Wang. *Spectroscopy of Condensed Media. Dynamics of Molecular Interactions* (Academic, 1985) [ISBN: 0-12-734780-1].
23. R.A. Kubo. Stochastic theory of line-shape and relaxation. In *Fluctuations, Relaxation and Resonance in Magnetic Systems*, edited by G. ter Haar (Oliver and Boyd, 1962).
24. S.A. Kirillov, M.I. Gorobets, D.O. Tretyakov, M.B. Ataev, M.M. Gafurov. Phase diagrams and conductivity of lithium salt systems in dimethyl sulfoxide, propylene carbonate and dimethyl carbonate. *J. Mol. Liq.* **205**, 78 (2015).
25. M.I. Gorobets, M.B. Ataev, M.M. Gafurov, S.A. Kirillov. Speciation in solutions of lithium salts in dimethyl sulfoxide, propylene carbonate, and dimethyl carbonate from raman data: a minireview. *J. Spectroscopy* **2016**, 1 (2016).
26. S.A. Kirillov. Time-correlation functions from band-shape fits without Fourier transform. *Chem. Phys. Lett.* **303**, 37 (1999).
27. P. Hobza, Z. Havlas. Improper, blue-shifting hydrogen bond. *Theor. Chem. Acc.* **108**, 325 (2002).
28. K. Hermansson. Blue-shifting hydrogen bonds. *J. Phys. Chem. A* **106**, 4695 (2002).
29. J. Joseph, E.D. Jemmis. Red-, blue-, or no-shift in hydrogen bonds: A unified explanation. *J. Am. Chem. Soc.* **129**, 4620 (2007).
30. S.A. Kirillov, M.I. Gorobets, M.M. Gafurov, M.B. Ataev, K.Sh. Rabadanov. Self-association and picosecond dynamics in liquid dimethyl sulfoxide. *J. Phys. Chem. B* **117**, 9439 (2013).
31. Y. Wang, P.B. Balbuena. Associations of alkyl carbonates: Intermolecular C-H...O interactions. *J. Phys. Chem. A* **105**, 9972 (2001).
32. P.A. Brooksby, W.R. Fawcett. Infrared (attenuated total reflection) study of propylene carbonate solutions containing lithium and sodium perchlorate. *Spectrochim. Acta Part A* **64**, 372 (2006).
33. J.E. Katon, M.D. Cohen. The vibrational spectra and structure of dimethyl carbonate and its conformational behavior. *Can. J. Chem.* **53**, 1378 (1975).
34. M. Takeuchi, N. Matubayasi, Y. Kameda, B. Minofar, S.-I. Ishiguro, Y. Umabayashi. Free-energy and structural analysis of ion solvation and contact ion-pair formation of Li<sup>+</sup> with BF<sub>4</sub><sup>-</sup> and PF<sub>6</sub><sup>-</sup> in water and carbonate solvents. *J. Phys. Chem. B* **116**, 6476 (2012).
35. J.-C. Soetens, C. Millot, B. Maigret, I. Baky. Molecular dynamics simulation and X-ray diffraction studies of ethylene carbonate, propylene carbonate and dimethyl carbonate in liquid phase. *J. Mol. Liq.* **201** (2001).
36. A.A. Kloss, W.R. Fawcett. ATR-FTIR studies of ionic solvation and ion-pairing in dimethylsulfoxide solutions of the alkali metal nitrates. *J. Chem. Soc., Faraday Trans.* **94**, 1587 (1998).
37. Z. Wang, B. Huang, S. Wang, R. Xue, X. Huang, L. Chen. Vibrational spectroscopic study of the interaction between lithium perchlorate and dimethylsulfoxide. *Electrochim. Acta* **42**, 2611 (1997).
38. X. Xuan, J. Wang, Y. Zhao, J. Zhu. Experimental and computational studies on the solvation of lithium tetrafluoroborate in dimethylsulfoxide. *J. Raman Spectrosc.* **38**, 865 (2007).
39. M.I.S. Sastry, S. Singh. Second derivative analysis of S=O stretching band in Raman spectra of dimethylsulphoxide in carbon tetrachloride and water. *Proc. Indian Acad. Sci. (Chem. Sci.)* **95**, 499 (1985).
40. A. Brodin, P. Jacobsson. Dipolar interaction and molecular ordering in liquid propylenecarbonate: Anomalous dielectric susceptibility and Raman non-coincidence effect. *J. Mol. Liq.* **164**, 17 (2011).
41. I.S. Perelygin, I.G. Itkulov, A.S. Krauze. Association of molecules of liquid propylene carbonate according to Raman spectroscopy. *Russ. J. Phys. Chem.* **66**, 573 (1992).
42. D. Battisti, G.A. Nazri, B. Klassen, R. Aroca. Vibrational studies of lithium perchlorate in propylenecarbonate solutions. *J. Phys. Chem.* **97**, 5826 (1993).
43. B. Collingwood, H. Lee, J.K. Wilmshurst. The structures and vibrational spectra of methylchloroformate and dimethylcarbonate. *Aust. J. Chem.* **19**, 1637 (1966).
44. S.A. Kirillov, E.A. Pavlatou, G.N. Papatheodorou. Instantaneous collision complexes in molten alkali halides: Picosecond dynamics from low-frequency Raman data. *J. Chem. Phys.* **116**, 9341 (2002).
45. S.A. Kirillov. Vibrational spectra of fused salts and dynamic criterion of complex formation in ionic liquids. *J. Mol. Struct.* **651–653**, 289 (2003).
46. J.M. Alía, H.G.M. Edwards. FT-Raman study of ionic interactions in lithium and silver tetrafluoroborate solutions in acrylonitrile. *J. Solut. Chem.* **29**, 781 (2000).
47. I.S. Perelygin, M.A. Klimchuk. Manifestation of interionic interactions in the IR absorption spectra of the tetrafluoroborate ion. *J. Appl. Spectrosc.* **50**, 207 (1989).

48. J.M. Alía, H.G.M. Edwards. Ion solvation and ion association in lithium trifluoromethanesulfonate solutions in three aprotic solvents. An FT-Raman spectroscopic study. *Vibrational Spectrosc.* **24**, 185 (2000).
49. I.S. Pereygin, G.P. Mikhailov, S.V. Tuchkov. Manifestations of ion-ion interaction in the Raman spectra of the trifluoromethanesulfonate ion. *J. Appl. Spectrosc.* **55**, 689 (1991).
50. M.I.S. Sastry, S. Singh. Raman spectral studies of solutions of alkali metal perchlorates in dimethyl sulfoxide and water. *Can. J. Chem.* **63**, 1351 (1985).
51. M. Chabanel, D. Legoff, K. Touaj. Aggregation of perchlorates in aprotic donor solvents. Part 1. Lithium and sodium perchlorates. *J. Chem. Soc., Faraday Trans.* **92**, 4199 (1996).
52. I.S. Pereygin, G.P. Mikhailov. Appearance of ion-ion interactions in the Raman scattering spectra of the perchlorate ion. *J. Appl. Spectrosc.* **49**, 713 (1988).
53. X. Guo, S.H. Tan, S.F. Pang, Y.H. Zhang. Measurement of the association constants through micro-Raman spectra of supersaturated lithium perchlorate droplets. *Sci. China Chem.* **56**, 1633 (2013).

Received 07.12.17

M.I. Горобець, С.О. Кириллов

ПІКОСЕКУНДНА ДИНАМІКА  
МОЛЕКУЛЯРНИХ ОБ'ЄКТІВ У РОЗЧИНАХ  
СОЛЕЙ ЛІТІУ В ДИМЕТИЛСУЛЬФОКСИДІ,  
ПРОПІЛЕНКАРБОНАТІ ТА ДИМЕТИЛКАРБОНАТІ

Резюме

Проведено аналіз спектрів комбінаційного розсіювання розчинів солей літію в диметилсульфоксиді, пропіленкарбонаті та диметилкарбонаті в діапазоні концентрацій від розведених розчинів до сумішей розплавлених сольватів з солями з точки зору динаміки, зокрема визначено та проаналізовано часи дефазування ( $\tau_V$ ) та модуляції ( $\tau_\omega$ ) всіх молекулярних об'єктів, присутніх у розчинах. Встановлено, що в пікосекундній часовій області процеси дефазування та модуляції в молекулах розчинника, зв'язаних водневим зв'язком з аніоном та/або сольватуючих катіон повільніші, ніж у молекулах вільного розчинника. В іонних парах, розділених розчинником, і  $\tau_V$ , і  $\tau_\omega$  є значно довшими, ніж у сольватованих аніонах, що свідчить про сильні взаємодії між аніонами та їх оточенням. У контактних іонних парах  $\tau_V$  є великими, тоді як  $\tau_\omega$  виявляються близькими до значень для вільних аніонів. Це відображає наближення структури рідини до структури розплавлених солей.