

L. Dobrzański

W. Borek

A. Zarychta

Division of Materials Processing
Technology, Management and
Computer Techniques
in Materials Science,
Institute of Engineering
Materials and Biomaterials,
Gliwice, Poland
leszek.dobrzanski@polsl.pl

UDK 621.178

HOT DEFORMATION AND RECRYSTALLIZATION OF HIGH-MANGANESE FE – MN – (AL, SI) TWIP STEEL

The new-developed high-manganese Fe – Mn – (Al, Si) steels provide an extensive potential for automotive industries through exhibiting the twinning induced plasticity (TWIP) phenomenon. Accordingly the characterization of hot deformation characteristics of this kind of steels is highly desired to optimize their formability. The aim of this paper is to determine the influence of hot deformation conditions on σ - ϵ curves and evolution of microstructure of TWIP steel with high manganese concentrations (26 mass%) and additions of aluminium and silicon (3 mass%). Additionally, the steels were microalloyed by Nb and Ti in order to control the grain growth under hot-working conditions. The force-energetic parameters of hot-working were determined in continuous and multi-stage compression test performed in temperature range of 850 to 1100°C using the DSI Gleeble 3800 thermo-mechanical simulator. Evaluation of processes controlling work-hardening were identified by microstructure observations of the specimens compressed to the various amount of deformation. Multi-stage compression tests with true strain of 0.29 permit to use the dynamic and metadynamic recrystallization for forming the fine-grained, austenite microstructure of steel in the whole range of deformation temperature. Making use of dynamic and metadynamic recrystallization, it is possible to refine the microstructure and to decrease the flow stress during the last deformation at 850°C. In case of applying the lower deformations 4×0.23 and 4×0.19 , the process controlling work hardening is dynamic recovery and a deciding influence on a gradual microstructure refinement has statical recrystallization. The obtained microstructure – hot-working relationships can be useful in the determination of powerful parameters of hot-rolling and to design a rolling schedule for high-manganese steel sheets with fine-grained austenitic structures.

TWIP steel, hot-working, recrystallization, grain refinement, compression test

Introduction. In the last few years attention of automotive industry is focused on modern high-strength steels, which allow to decrease the weight of different elements of vehicles, what is directly connected with lowering fuel consumption and limiting of harmful exhaust gas emission.

Presently, the most advanced steels predicted to be used for the most challenging car components with a complex shape and absorbing energy in crash events are high-manganese austenitic TRIP/TWIP steels (Allain et al., 2004, Frommeyer et al., 1998, 2003, 2009, Grässel et al., 2000, Kim et al., 1989).

High-manganese austenitic steels consist of 15 to 30% of manganese, from 0.02 to 0.1% of carbon and about 3% of aluminium and 3% of silicon, among others, in order to decrease density which for this group of steels is about 7.3 g/cm³. The function of silicon and aluminium is solution hardening of the steel, and carbon is an element that stabilizes austenite. These steels achieve profitable group of mechanical properties, i.e. (ultimate tensile strength) UTS = 600÷900 MPa, (yield strength) YS_{0.2} = 250÷450 MPa, (uniform elongation) UE1 = 35÷80% which strongly depends on chemical composition, especially concentration of Mn (Frommeyer et al., 1998, 2003, Vercammen et al., 2004). Mechanical properties of high-manganese austenitic steels also depend on structural processes present during cold plastic deformation, which in turn are the derivative of stacking fault energy of austenite (Frommeyer et al., 2003). Silicon and aluminium have also influence on the stacking fault energy of austenite, deciding about a type of deformation mechanism during plastic deformation. In case stacking fault energy (SFE) is equal from 12 to 20mJm⁻², partial transformation of austenite into martensite occurs making use of TRIP effect (Transformation Induced Plasticity) (Grassel et al., 2000). Values of SFE from 20 to 60mJm⁻² determine intense course of mechanical twinning connected to TWIP effect (Twinning Induced Plasticity) (Vercammen et al., 2004).

Developing production technology of high-manganese austenitic steels require knowledge about their behaviour during hot plastic strain. There is a shortage of sufficient information content in science publication. There are only a few papers related with behaviour of Fe-Cr-Mn, Fe-Mn and Fe-Mn-Al steels during hot plastic deformation (Hamada et al., 2007a, 2007b, Niewielski, 2000, Niewielski et al., 2003, Sabet et al., 2008). Initial investigations on high-manganese steels containing silicon and aluminium showed that new-developed steels are characterized by high values of flow stresses but at relatively low values of strain ϵ_{\max} corresponding to maximum values of flow stress (Dobrzański et al., 2008a, 2008b, 2008c, 2009, Sabet et al., 2008). Hamada et al. (2007a, 2007b) were found that maximal flow stress at a temperature of 1100°C for 25Mn steel occurs for $\epsilon_{\max} = 0.17$, what allows to refine the steel microstructure by the use of the dynamic recrystallization. Increasing concentration of Al caused displacement ϵ_{\max} to a value about 0.28. Moreover steel which contains Al has a higher plastic flow stress than 25Mn steel. Application of thermo-mechanical treatment consisting in immediate cooling of steel from a finishing temperature of multi-stage hot-working in controlled conditions (Dobrzański et al., 2008b) should also allow to form a fine-grained microstructure of new-developed C-Mn-Si-Al steel containing Nb and Ti microadditions. To develop rolling procedures, it is important to reflect real temperature-strain hot-working conditions and also to determine the microstructure evolution in successive stages of hot plastic deformation. It's foreseen that structure diversification after different kind of thermo-mechanical treatment should have influence on behaviour of that group of steels in further cold plastic strain conditions.

2. Experimental procedure. The examinations were performed on new-developed high-manganese austenitic 26Mn-3Si-3Al-Nb-Ti steel, containing Nb and Ti

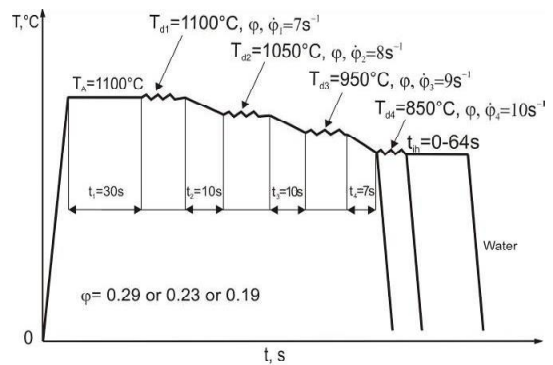


Fig. 1. Parameters of the multi-stage compression test realized in the Gleeble 3800 simulator

microadditions (Table 1). Melts were prepared in the Balzers VSG-50 vacuum induction furnace. After homogenization at 1200°C for 4 h, in order to remove the segregation of Mn, ingots with a mass of 25kg were submitted for open die forging on flats with a width of 220 mm and a thickness of 20 mm. Then, cylindrical machined samples $\varnothing 10 \times 12$ mm were made. In order to determine the influence of temperature on a steel grain growth, samples were solution heat-treated in water from the austenitizing temperature in a range from 900 to 1100°C.

Determination of processes controlling work hardening was carried out in continuous axisymmetrical compression test using the DSI Gleeble 3800 thermomechanical simulator. The stress – strain were defined in a temperature range from 850 to 1050°C with a strain rate of 10s⁻¹. Depending on loads possible to apply in specific rolling schedules, it is important to determine σ - ϵ curves for various values of reduction. In purpose of mentioned above, the sequences of true strains for successive variants of deformation were equal: 4x0.29, 4x0.23 and 4x0.19 (Fig. 1). Multi-stage compression tests were also carried out using Gleeble 3800 thermomechanical simulator. The specimens were inserted in a vacuum chamber, where they were resistance-heated. Tantalum foils were used to prevent sticking of sample with a die and graphite foils as a lubricant. Identification of microstructure evolution was performed through samples quenched in water in successive stages of deformation and after isothermal holding the samples for the time up to 64s in a temperature of finishing deformation (850°C).

Metallographic examination of samples with specification of grain size and mass of recrystallized austenite fraction were carried out on light microscope LEICA MEF4A. Mass of recrystallized austenite fraction was determined in the area of 1/3 radius from the centre of the sample. In order to disclose austenite grain boundary, samples etched in mixture of nitrous and hydrochloric acid in proportions 2:1 and in mixture HNO₃, HCl and H₂O in proportions 2:2:1. X-ray diffraction analysis of specimens in the initial state and after various stages of deformation was carried out using the Co K α radiation in the X'Pert PRO diffractometer with the X'Celerator strip detector.

3. Results and discussion. The new-developed steel in the initial state is characterized by homogeneous microstructure of austenite with a grain size equal approximately 100 μ m, in which numerous annealing twins can be identified (Fig. 2a). Single-phase microstructure of the steel is confirmed by X-ray diffraction pattern in Fig. 2b.

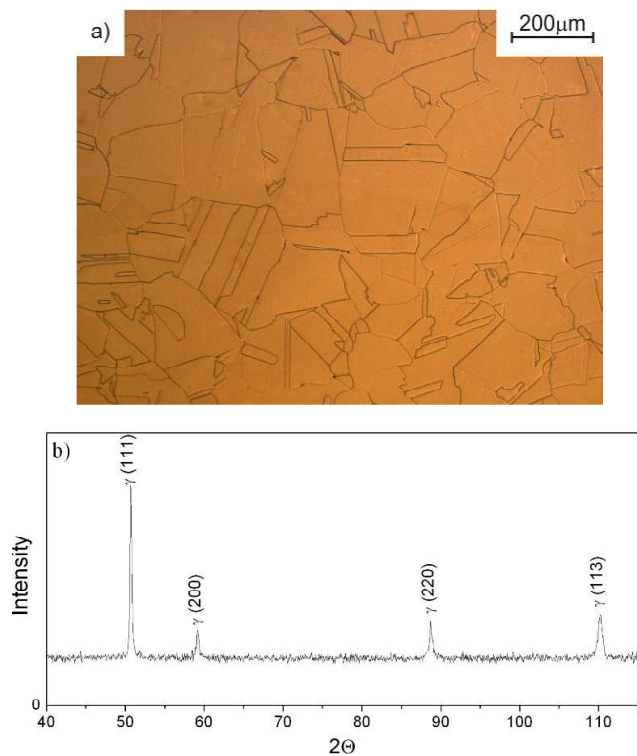


Fig. 2. Austenitic microstructure with numerous annealing twins of the 26Mn-3Si-3Al-Nb-Ti steel in the initial state (a) and X-ray diffraction pattern (b)

Starting points for microstructure analysis of specimens that were plastically hot-deformed in variable conditions are microstructures of steel subjected to solution heat treatment from a temperature range of 900 to 1000°C. The steel possesses fine-grained microstructure of austenite with grain sizes from 12 to about 22 μm up to temperature of 1000°C (Fig. 3). Further increase in solutioning temperature to 1100°C results in a rapid grain growth up to about 50 μm. The fine-grained microstructure is due to the advantageous influence of dispersive particles of (Nb,Ti)(C,N) limiting the steel grain growth, what was investigated elsewhere (Dobrzański et al., 2008c). Moreover, numerous annealing twins can be observed in the microstructure (Fig. 3).

Stress-strain curves obtained in continuous compression tests is presented in Fig. 4. This test allowed determine the

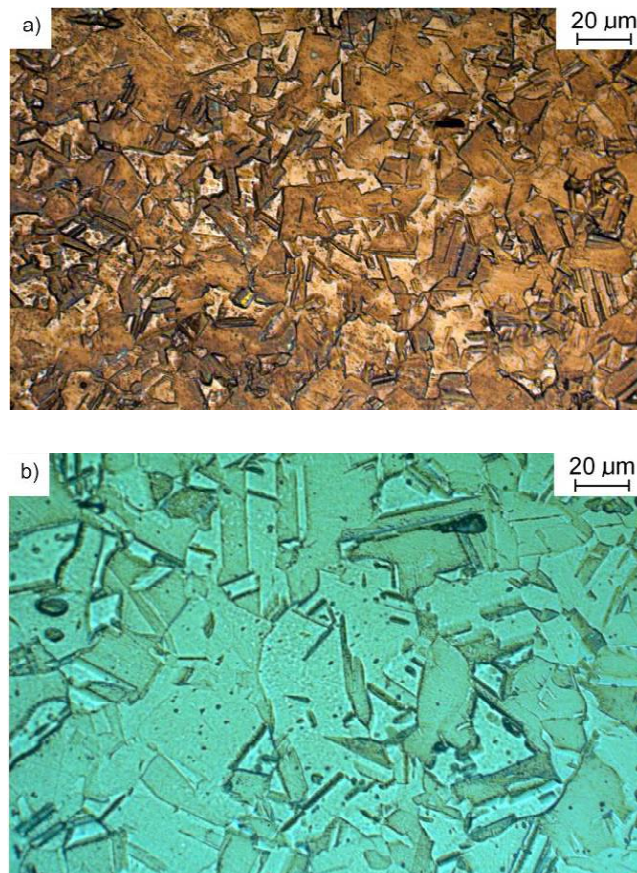


Fig. 3. Austenitic structures of the steel 26Mn-3Si-3Al-Nb-Ti after solution heat treatment from a temperature: a) 900°, b) 1000°C

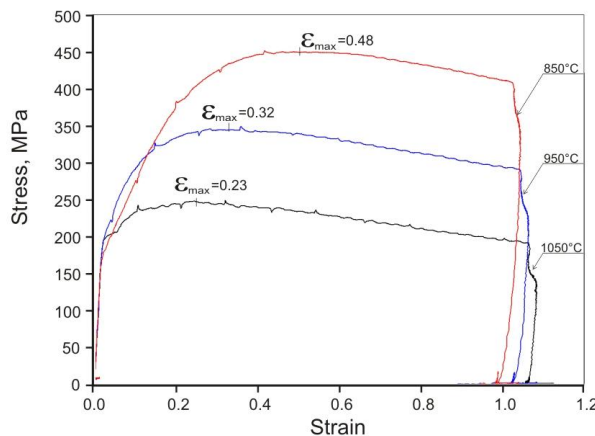


Fig. 4. Influence of the temperature on a shape of y-e curves for the specimens compressed with a strain rate of 10s⁻¹

Table 1

Chemical composition of the investigated steels, mass contents, %

Designation	26Mn-3Si-3Al-Nb-Ti
C	0.065
Mn	26.0
Si	3.08
Al	2.87
P	0.004
S	0.013
Nb	0.034
Ti	0.009
N	0.0028

range of flow stress of investigated steel in a temperature range from 1050°C to 850°C. It arises from Fig. 4 that the steel 26Mn-3Si-3Al-Nb-Ti is characterized by values of flow stress equal from 250 to 430 MPa in investigated range of temperature.

These values are considerably higher than they are for conventional C-Mn steels and for Cr-Ni and Cr-Mn austenitic steels (Niewielski et al., 2003). It proves high work-hardening, which is caused by high Mn concentration in the steel. Additionally, the increase of flow stress is influenced by Si

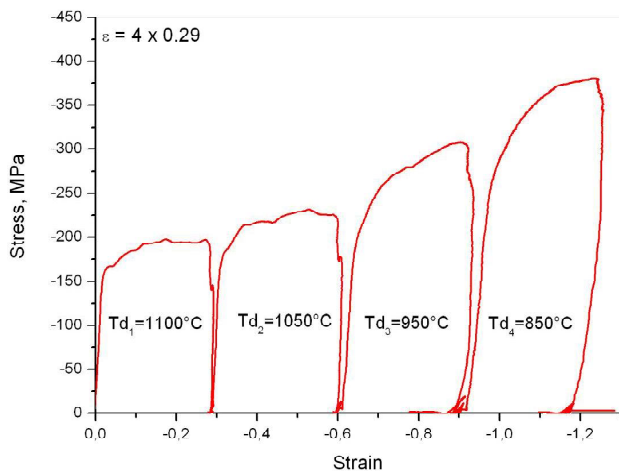


Fig. 5. Stress - strain curves after the multi-stage compression test of the axisymetrical specimens deformed with a true strain 4×0.29 in a temperature range from 1100 to 850°C

and Al as well as Nb and Ti microadditions. Increase of flow stress along with decrease of compression temperature is

accompanied by translation of ϵ_{\max} strain in the direction of higher deformations. It is characteristic, that after strong strain hardening, peaks of ϵ_{\max} are present for relatively low strain values, i.e. from 0.24 to 0.46. It creates convenient conditions for using dynamic recrystallization for refinement of microstructure. Initiation of dynamic recrystallization in a temperature range up to 950°C requires a relatively small strain value of about 0.32, often applied in rolling schedules. Lowering the deformation temperature to 850°C results in a considerable increase of the critical strain to about 0.46.

Stress-strain curves of the steel plastically deformed according to the scheme shown in Fig. 1 are presented in Fig. 5. Application of true strain equal 0.29 during multi-stage compression creates possibility of the course of dynamic recrystallization, what is indicated by peaks that can be distinguished on σ - ϵ curves – especially for deformations realized at temperature of 1100 and 1050°C. After decreasing deformation temperature, maximum on σ - ϵ curves is present for a maximum value of true strain (0.29). The values of flow stress in the range of deformation temperature from 1100 to 950°C are comparable with values obtained in continuous compression test. Cyclic deformation and a partially

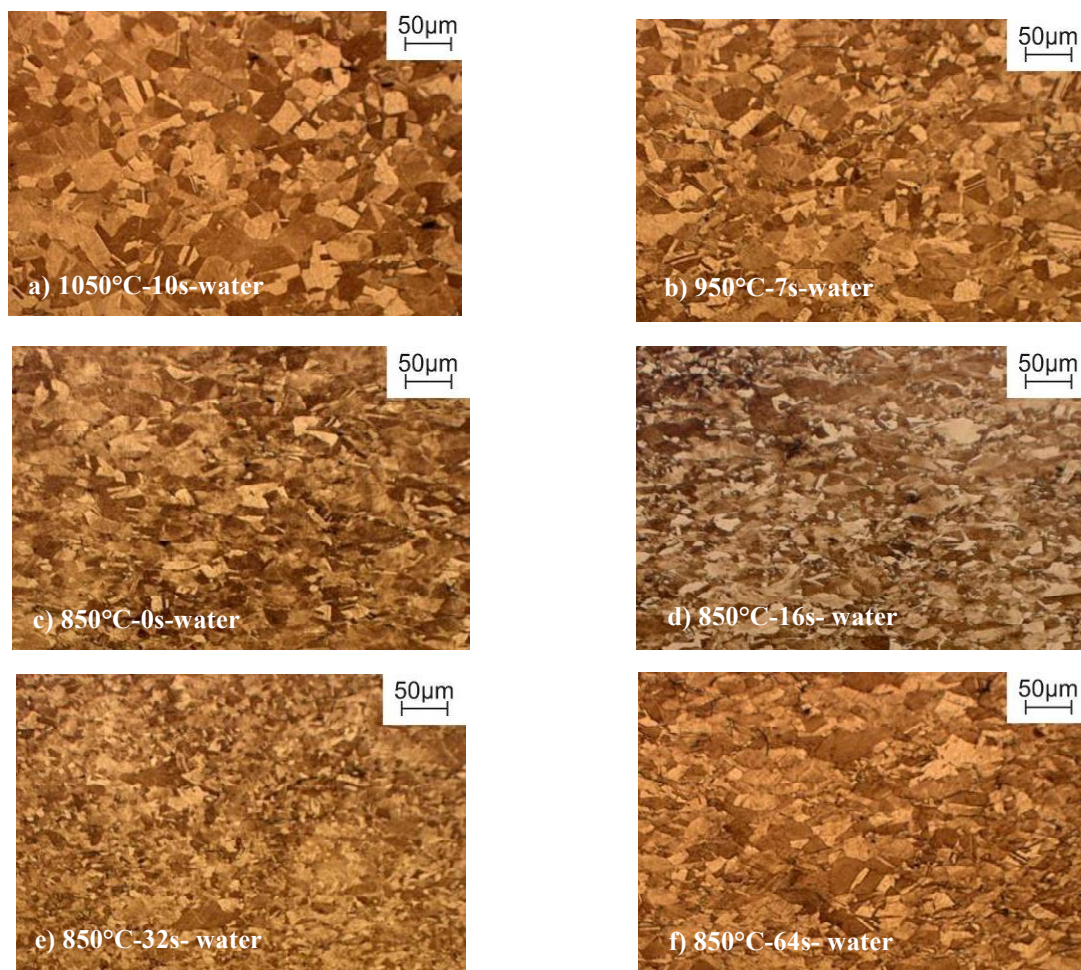


Fig. 6. Austenitic structures obtained after solutioning the steel in successive stages of the hot-working for the specimens compressed to a true strain 4×0.29 and isothermally held for the time from 0 to 64s: a) metadynamically recrystallized grains during the interval between second and third deformation, b) metadynamically recrystallized grains during the interval between third and fourth deformation, c) initiation of dynamic recrystallization, d) grain refinement due to metadynamic and static recrystallization, e) fine statically recrystallized austenite grains, f) grain growth as a result of metadynamic recrystallization

recrystallization between successive deformations result in a much faster maximum on the σ - ε curve for the fourth deformation compared to the curve obtained at a temperature of 850°C in the continuous compression test (Fig. 5).

Microstructures of steel in the successive deformation stages and after its finish corresponding to σ - ε curves are put together in Fig. 6a-f. After deformation of the specimen at a temperature of 1050°C and subsequent cooling for 10s

corresponding to the interpass time, the steel is characterized by uniform, metadynamically recrystallized austenite microstructure with a grain size of about 40 μm (Fig. 6a).

Lowering the deformation temperature to 950°C and the time of 7s for cooling the specimen to 850°C results in much smaller fraction of metadynamically recrystallized grains located in a matrix of statically recovered grains (Fig. 6b). A partial removal of work-hardening through metadynamic

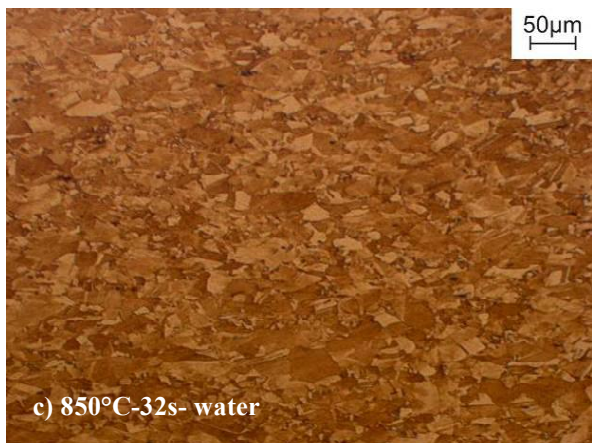
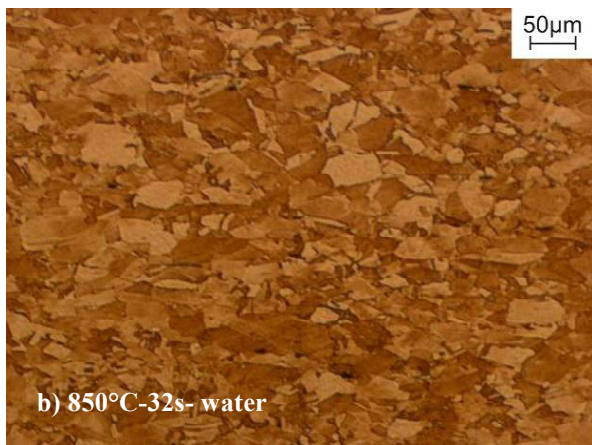
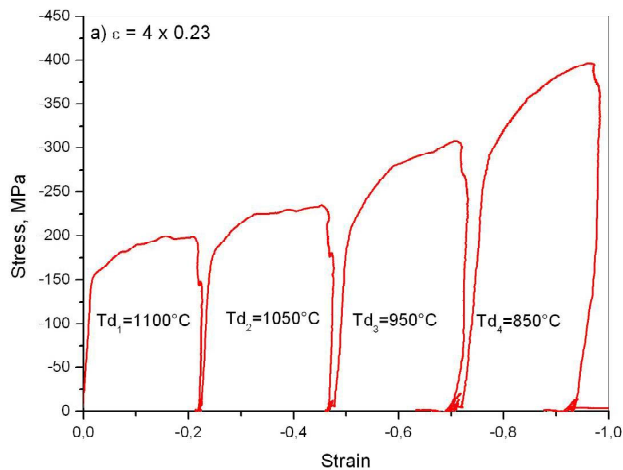


Fig. 7. Stress - strain curves after the multi-stage compression test of the axisymetrical specimens deformed with a true strain 4×0.23 in a temperature range from 1100 to 850°C (a), and statically recrystallized austenitic structures of the steel 26Mn-3Si-3Al-Nb-Ti obtained after solutioning the specimen after isothermal holding the steel for 32s in a last deformation temperature of 850°C (b), (c)

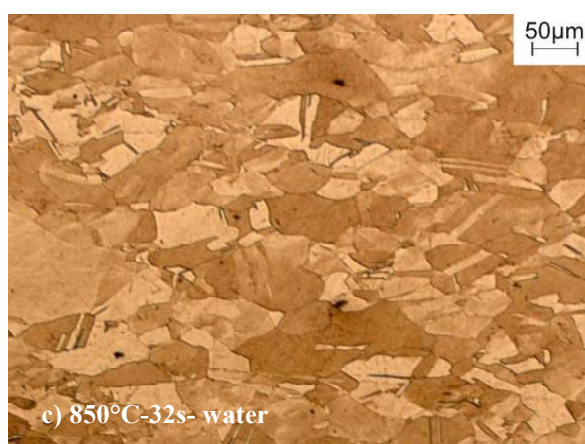
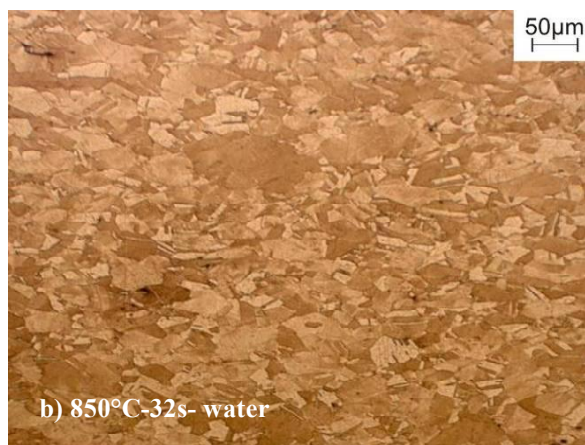
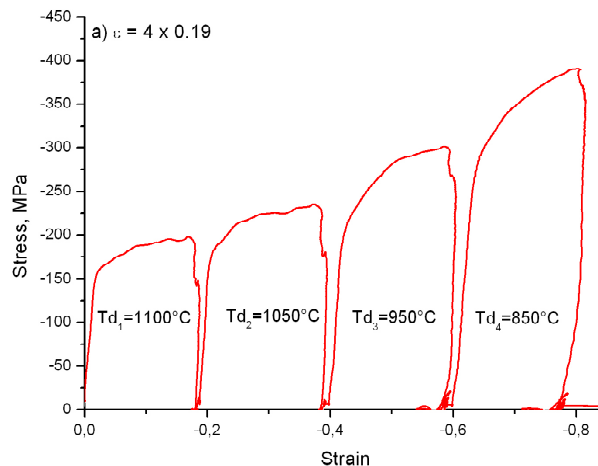


Fig. 8. Stress - strain curves after the multi-stage compression test of the axisymetrical specimens deformed with a true strain 4×0.19 in a temperature range from 1100 to 850°C (a), and austenitic structures of the steel 26Mn-3Si-3Al-Nb-Ti in an initial stage of static recrystallization obtained after solutioning the specimen after isothermal holding the steel for 32s in a last deformation temperature of 850°C (b), (c)

recrystallization that occurs during the interval between third and fourth deformation is a result of significant decrease of flow stress noted for the last deformation realized at the temperature of 850°C (Fig. 5), compared

to the curve obtained in the continuous compression test (Fig. 4). Additionally, cyclic deformations as well as the course of partial recrystallization cause much faster achievement of maximum on σ - ε curve for the fourth deformation when comparing to continuous compression at the temperature of 850°C.

The initiation of dynamic recrystallization during the last deformation at a temperature of 850°C is confirmed by a micrograph in Fig. 6c, showing a partially recrystallized austenite with a grain size of about 20 μm . Isothermal holding of the specimen in a temperature of the last deformation for 16s leads to a remarkably fine-grained metadynamically recrystallized austenite microstructure with a fraction of about 40%, located in the matrix of slightly elongated, statically recovered grains containing numerous annealing twins (Fig. 6d).

Further extension of holding time to 32s leads to obtaining almost fully recrystallized microstructure of steel (Fig. 6e) with a mean austenite grain size of about 10 μm . Holding of steel in the deformation temperature for 64s causes gradual increase of recrystallized grains sizes (Fig. 6f).

Decrease of true strain to 0.23 during the multi-stage compression test leads to changes of the course of stress-strain curves (Fig. 7a). A shape of the curves during deformation in a temperature range of 1100-1050°C and true stress values are comparable to that obtained after higher strain applying. Moreover, the applied strain is sufficient to initiate a course of dynamic recrystallization. However, decreasing the compression temperature to 950°C causes that the flow stress is slightly higher and the applied strain value is too low to initiate dynamic recrystallization. Thus, process controlling a course of hot-working at 950°C is a dynamical recovery.

Because of a lack of dynamic recrystallization in final passes, a refinement of microstructure requires the use of thermally activated, static processes removing work-hardening. For instance, the micrographs in Fig. 7b, 7c show the austenite microstructure of the steel isothermally held for 32 s at 850°C after compression with a true strain of 4x0.23. The fraction of statically recrystallized austenite equals approximately 50% (Fig. 7b). Numerous annealing twins can be observed in the microstructure (Fig. 7c) and a mean statically recrystallized austenite grain is higher compared to the specimen compressed 4x0.29, where a reconstruction of the microstructure was obtained both in static and metadynamic processes (Fig. 6e).

Further decrease of true strain to 0.19 causes that dynamic recovery is the process controlling work hardening in the whole temperature range of deformation (Fig. 8a), at similar values of flow stress in comparison with the specimen deformed 4x0.23. However, the isothermal holding of the specimen for 32s is too short to obtain a desired fraction of recrystallized phase, which equals approximately 20% (Fig. 8b). Once again, numerous annealing twins can be observed in microstructure and fine statically recrystallized grains of γ phase are located mainly on boundaries of elongated statically recovered austenite grains (Fig. 8c).

4. Conclusions. On the basis of the investigations carried out in the initial state and under conditions of the continuous and multi-stage compression, the following conclusions can be drawn:

- The new-developed high-manganese steel is characterized by homogeneous austenite structure with many annealing twins.

- Solutioning the steel does not change its phase composition but has essential effect on a grain size of austenite, which is fine-grained up to a temperature of about 1000°C.

- The hot-working resistance of the steel is much higher in comparison with austenitic Cr-Ni and Cr-Mn steels and slightly higher compared to binary Fe-Mn alloys. The flow stresses are in the range of 200-430 MPa for the applied conditions of hot-working and are up to 40 MPa lower compared to continuous compressions.

- The best conditions for a gradual grain refinement occur after four-stage compression with the true strain of 4x0.29 in hot-working conditions controlled by dynamic recrystallization in a whole temperature deformation range. The steel solutioned directly after deformation is characterized by a mixture of fine, recrystallized grains and some fraction of dynamically recovered grains with a mean diameter of about 10 μm . Completing recrystallization in all the deformed grains requires isothermal holding of the specimen for 32 s at 850°C. The refinement of austenite microstructure proceeds by metadynamic recrystallization.

- Decreasing the true strain to 4x0.23 and 4x0.19 changes a main mechanism controlling a course of work hardening from dynamic recrystallization to dynamic recovery. A relatively small fraction of recrystallized phase between successive passes is a reason of higher flow stresses up to 400 MPa in a final deformation temperature. Due to slow progress of static recrystallization, the isothermal holding of the specimens at 850°C for 32 s results in a small fraction of recrystallized austenite and a larger size of flattened, statically recovered grains.

5. Acknowledgements. Scientific work was partially financed from the science funds in the framework of project No. N N507 287936 headed by Prof. L.A. Dobrzański.

The authors would like to express their gratitude to Prof. R. Kuziak from Institute for Ferrous Metallurgy in Gliwice for carrying out the experiments using the Gleeble 3800 simulator.

References

1. Allain, S., Chateau, J.P., Bouaziz, O., Migot, S. and Guelton, N., 2004, "Correlations between the calculated stacking fault energy and the plasticity mechanisms in Fe-Mn-C alloys", *Materials Science and Engineering A*, Vol. 387-389, pp. 158-162.
2. Dobrzański, L.A., Grajcar, A. and Borek, W., 2008a, "Influence of hot-working conditions on a structure of high-manganese austenitic steels", *Journal of Achievements in Materials and Manufacturing Engineering*, Vol. 29, pp. 139-142.
3. Dobrzański, L.A., Grajcar, A. and Borek, W., 2008b, "Hot-working behaviour of high-manganese austenitic steels",

Journal of Achievements in Materials and Manufacturing Engineering, Vol. 31, Issue 1, pp. 7-14.

4. Dobrzański, L.A., Grajcar, A. and Borek, W., 2008c, "Microstructure evolution and phase composition of high-manganese austenitic steels", Journal of Achievements in Materials and Manufacturing Engineering,

Vol. 31, Issue 2, pp. 218-225.

5. Dobrzański, L.A., Grajcar, A. and Borek, W., 2009, "Microstructure evolution of high-manganese steel during the thermo-mechanical processing", Archives of Materials Science and Engineering, Vol. 37, pp. 69-76.

6. Frommeyer, G., Brück, U., Brokmeier, K. and Rablbauer, R., 2009, "Development, microstructure and properties of advanced high-strength and supraductile light-weight steels based on Fe-Mn-Al-Si(C)", Proceedings of the 6th International Conference on Processing and Manufacturing of Advanced Materials, Thermec'2009, Berlin, p. 162.

7. Frommeyer, G., Brück, U. and Neumann, P., 2003, "Supra-ductile and high-strength manganese-TRIP/TWIP steels for high energy absorption purposes", ISIJ International Vol. 43, pp. 438-446.

8. Frommeyer, G. and Grässel, O., 1998, "High strength TRIP/TWIP and superplastic steels: development, properties, application", La Revue de Metallurgie-CIT 10, pp. 1299-1310.

9. Grässel, O., Krüger, L., Frommeyer, G. and Meyer, L.W., 2000 "High strength Fe-Mn-(Al, Si) TRIP/TWIP steels development – properties – application", International Journal of Plasticity Vol. 16, pp. 1391-1409.

10. Hamada, A.S., Karjalainen, L.P. and Somani, M.C., 2007a, "The influence of aluminium on hot deformation behaviour and tensile properties of high-Mn TWIP steels", Materials Science and Engineering A, Vol. 467, pp. 114-124.

11. Hamada, A.S., Karjalainen, L.P. Somani, M.C. and Ramadan, R.M., 2007b, "Deformation mechanisms in high-Al bearing high-Mn TWIP steels in hot compression and in tension at low temperatures", Materials Science Forum Vol. 550, pp. 217-222.

12. Kim, Y.G., Han, J.M. and Lee, J.S., 1989, "Composition and temperature dependence of tensile properties of austenitic Fe-Mn-Al-C alloys", Materials Science and Engineering A, Vol. 114, pp. 51-59.

13. Niewielski, G., 2000, "Changes of structure and properties of austenitic steel caused by hot deformation", Scientific Books of the Silesian University of Technology 58, The Silesian University of Technology Publishers, Gliwice, (in Polish).

14. Niewielski, G., Hetmańczyk, M. and Kuc, D., 2003, "Influence of the initial structure and deformation conditions on properties of hot-deformed austenitic steels", Materials Engineering, Vol. 24, pp. 795-798, (in Polish).

15. Sabet, M., Zarei-Hanzaki, A. and Khoddam, S., 2008, "An investigation to the hot deformation behaviour of high-Mn TWIP steels", 3rd International Conference on Thermomechanical Processing of Steels, TMP'2008, (CD-ROM), Padua, pp. 1-7.

16. Vercammen, S., Blanpain, B., De Cooman, B.C. and Wollants, P., 2004, "Mechanical behaviour of an austenitic Fe-30Mn-3Al-3Si and the importance of deformation twinning", Acta Materialia Vol. 52, pp. 2005-2012.

Отримана 25.04.11

L. Dobrzański, W. Borek, A. Zarychta

Hot deformation and recrystallization of high-manganese Fe – Mn – (Al, Si) TWIP steel

Division of Materials Processing Technology, Management and Computer Techniques in Materials Science, Institute of Engineering Materials and Biomaterials, Gliwice, Poland

The new-developed high-manganese Fe – Mn – (Al, Si) steels provide an extensive potential for automotive industries through exhibiting the twinning induced plasticity (TWIP) phenomenon. Accordingly the characterization of hot deformation characteristics of this kind of steels is highly desired to optimize their formability. The aim of this paper is to determine the influence of hot deformation conditions on σ - ϵ curves and evolution of microstructure of TWIP steel with high manganese concentrations (26 mass%) and additions of aluminium and silicon (3 mass%). Additionally, the steels were microalloyed by Nb and Ti in order to control the grain growth under hot-working conditions. The force-energetic parameters of hot-working were determined in continuous and multi-stage compression test performed in temperature range of 850 to 1100°C using the DSI Gleeble 3800 thermo-mechanical simulator. Evaluation of processes controlling work-hardening were identified by microstructure observations of the specimens compressed to the various amount of deformation. Multi-stage compression tests with true strain of 0.29 permit to use the dynamic and metadynamic recrystallization for forming the fine-grained, austenite microstructure of steel in the whole range of deformation temperature. Making use of dynamic and metadynamic recrystallization, it is possible to refine the microstructure and to decrease the flow stress during the last deformation at 850°C. In case of applying the lower deformations 4×0.23 and 4×0.19 , the process controlling work hardening is dynamic recovery and a deciding influence on a gradual microstructure refinement has statical recrystallization. The obtained microstructure – hot-working relationships can be useful in the determination of powerful parameters of hot-rolling and to design a rolling schedule for high-manganese steel sheets with fine-grained austenitic structures.

Інформація

8th European Solid Mechanics Conference

9 July 2012 — 13 July 2012 Graz, Austria

Contact: Prof. G.A. Holzapfel

E-mail: holzapfel@tugraz.at

Information: Two joint EUROMECH-ECCOMAS mini-symposia on "Science and Technology of Composites Manufacturing Processes" and "Virtual Testing of Composites"